

FDM Nylon 12CF



FDM Thermoplastic Filament

The information presented are typical values intended for reference and comparison purposes only.
They should not be used for design specifications or quality control purposes.



Overview

FDM® Nylon 12CF™ is a PA12 (polyamide 12) thermoplastic filament reinforced with chopped carbon fiber, 35% by weight. It has the highest flexural strength of any FDM thermoplastic, resulting in the highest stiffness-to-weight ratio. The combination of high strength, stiffness and light weight makes it an optimal replacement for heavier metal components in appropriate use cases.

Typical applications include strong, lightweight tooling, functional prototyping and select end-use parts.

Contents:

Ordering Information	3
Physical Properties	4
Mechanical Properties	5
Appendix	7

Ordering Information

Table 1. Printer and Support Material Compatibility

Printer	Model Tip (Slice)	Support Material	Support Tip
Fortus 450mc™	T20C (10 slice)	SR-110™ (soluble)	T12SR100
Fortus 380mc™ CFE ¹	T20C (10 slice)	SR-110 (soluble)	T12SR100
F900™	T20C (10 slice)	SR-110 (soluble)	T12SR100

¹ CFE – Carbon Fiber Edition.

Build Sheet

Nylon

- 0.02 x 26 x 38 in.
- 0.02 x 16 x 18.5 in.
- 0.02 x 14 x 16.5 in.

Hardware

Due to the high abrasion of this material, a system upgrade is required to support a hardened head and drive wheels. Ordering information can be found in Table 2.

Table 2. FDM Nylon 12CF Ordering Information

Part Number	Description
Filament Canisters	
355-02411	FDM Nylon 12CF, 92.3 cu in. - Plus
355-03130	SR-110 Soluble Support, 92.3 cu in. - Plus
Printer Consumables	
511-10720	T20C tip
511-10100	T12SR100 tip
325-00600	Nylon build sheet, 0.2 x 26 x 38 in. (0.76 x 660 x 965 mm)
325-00700	Nylon build sheet, 0.2 x 16 x 18.5 in. (0.76 x 406 x 470 mm)
355-00700	Nylon build sheet, 0.2 x 16 x 16.5 in. (0.76 x 406 x 420 mm)
System Upgrades	
335-60000	Fortus 900mc Gen 3 Upgrade from Gen 1 & 2 Systems
325-63500	Hardened F900 Head Only

Physical Properties

Values are measured as printed. XY, XZ, and ZX orientations were tested. For full details refer to the [Stratasys Materials Test Report](#) (immediate download upon clicking the link). DSC and TMA curves can be found in the Appendix.

Table 3. FDM Nylon 12CF Physical Properties


Property	Test Method	Typical Values		
		XY	XZ/ZX	
HDT @ 66 psi	ASTM D648	160 °C (320 °F)	168 °C (335 °F)	
	Method B			
HDT @ 264 psi	ASTM D648	130 °C (266 °F)	154 °C (309 °F)	
	Method B			
Tg	ASTM D7426	38 °C (100 °F)		
	Inflection Point			
Mean CTE	ASTM E831	155 µm/[m*°C] (86 µin./[in.*°F])	37 µm/[m*°C] (21 µin./[in.*°F])	
	(-50 °C to 20 °C)			
Mean CTE	ASTM E831	180 µm/[m*°C] (100 µin./[in.*°F])		
	(20 °C to 60 °C)			
Mean CTE	ASTM E831	195 µm/[m*°C] (108 µin./[in.*°F])		
	(60 °C to 115 °C)			
Mean CTE	ASTM E831	295 µm/[m*°C] (164 µin./[in.*°F])		
	(115 °C to 150 °C)			
Mean CTE	ASTM E831		46 µm/[m*°C] (26 µin./[in.*°F])	
	(20 °C to 105 °C)			
Mean CTE	ASTM E831		58 µm/[m*°C] (32 µin./[in.*°F])	
	(105 °C to 150 °C)			
Volume Resistivity	ASTM D257	3*10^7 Ω*cm		
Dielectric Constant	ASTM D150	Too conductive		
	1 kHz test condition			
Dielectric Constant	ASTM D150	11.4	10.0	
	2 MHz test condition			
Dissipation Factor	ASTM D150	Too conductive		
	1 kHz test condition			
Dissipation Factor	ASTM D150	0.100	0.000	
	2 MHz test condition			
Specific Gravity	ASTM D257	1.19		
	@23 °C			

Mechanical Properties

FDM Nylon 12CF samples were printed with a 0.010 in. (0.254 mm) layer height on the F900. For the full test procedure please see the [Stratasys Materials Test Procedure](#) (immediate download upon clicking the link).


Print Orientation

Parts created using FDM are anisotropic as a result of the printing process. Below is a reference of the different orientations used to characterize the material.

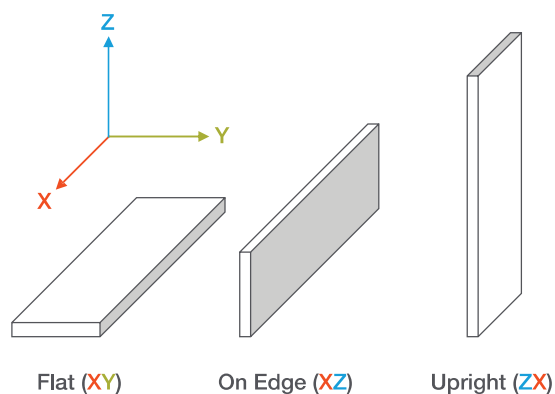

Tensile Curves

Due to the anisotropic nature of FDM, tensile curves look different depending on orientation. Below is a guide of the two types of curves seen when printing tensile samples and what reported values mean.

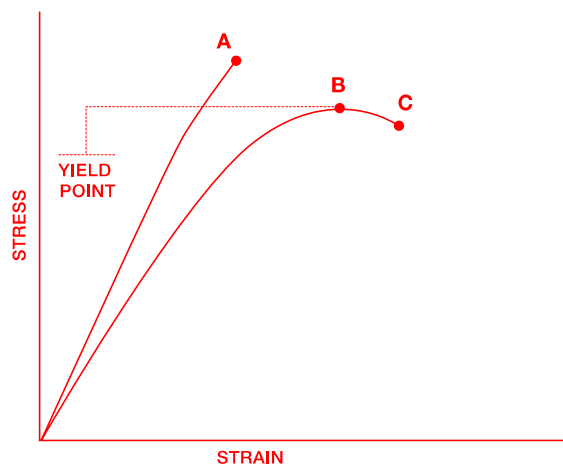

A = Tensile at break, elongation at break (no yield point)

B = Tensile at yield, elongation at yield

C = Tensile at break, elongation at break

Table 4. FDM Nylon 12CF Mechanical Properties (Fortus 450mc - T20C tip)

		XZ Orientation ¹	ZX Orientation ¹
Tensile Properties: ASTM D638			
Yield Strength	MPa	No yield	No yield
	psi	No yield	No yield
Elongation @ Yield	%	No yield	No yield
Strength @ Break	MPa	83 (2)	33 (4)
	psi	12,110 (250)	4,745 (510)
Elongation @ Break	%	2.4 (0.3)	1.2 (0.2)
Modulus (Elastic)	GPa	9.5 (0.6)	3.0 (0.4)
	ksi	1,380 (95)	434 (62)
Flexural Properties: ASTM D790, Procedure A			
Strength @ Break	MPa	150 (2)	62 (3)
	psi	22,245 (310)	9,070 (490)
Strain @ Break	%	2.7 (0.1)	3.1 (0.2)
Modulus	GPa	11.1 (0.3)	2.3 (0.1)
	ksi	1,610 (40)	340 (12)
Compression Properties: ASTM D695			
Yield Strength	MPa	110 (3)	140 (3)
	psi	15,975 (440)	20,425 (380)
Modulus	GPa	6.8 (0.5)	3.7 (0.1)
	ksi	980 (80)	530 (15)
Impact Properties: ASTM D256, ASTM D4812			
Notched	J/m	105 (7)	25 (3)
	ft*lb/in.	2.0 (0.1)	0.45 (0.06)
Unnotched	J/m	345 (40)	120 (20)
	ft*lb/in.	6.5 (0.7)	2.3 (0.3)

¹ Values in parenthesis are standard deviations.

Appendix

Figure 1. 2nd heating scan DSC data for the Nylon 12CF Flat (XY) sample.

DSC

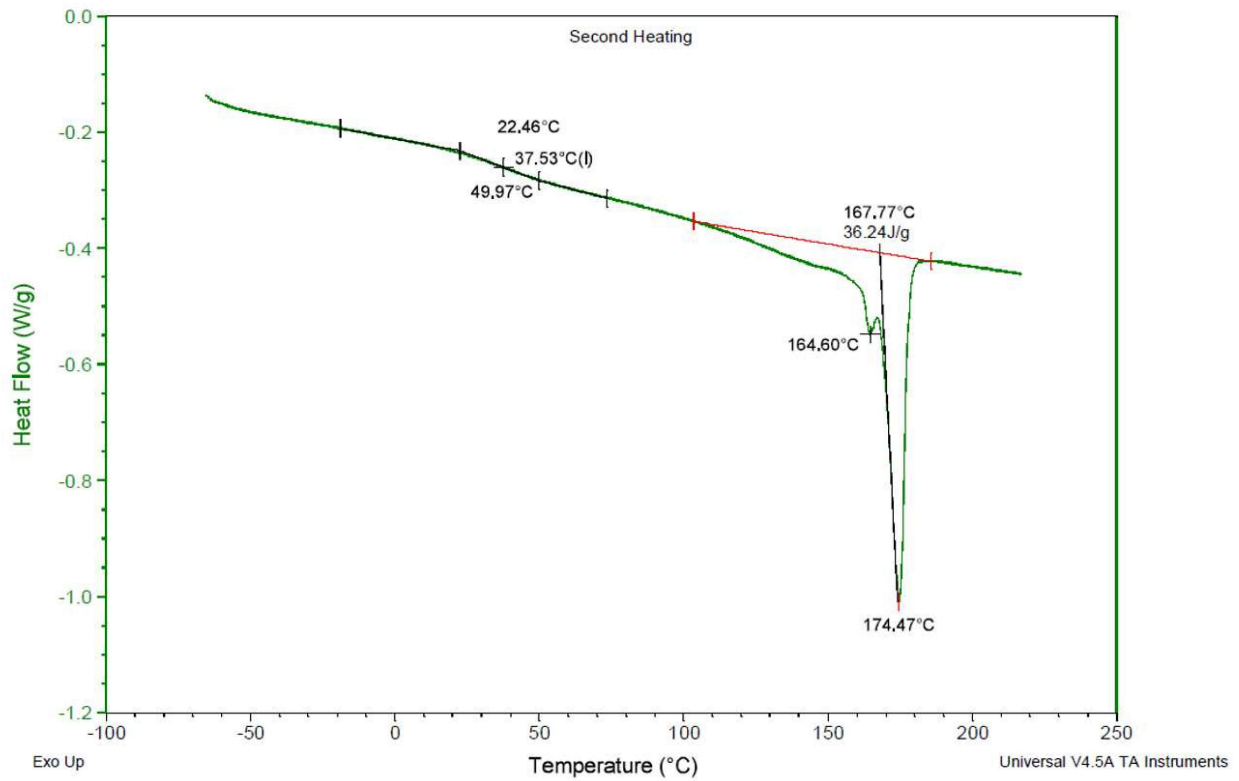


Figure 2. Dimension change data as a function of temperature for the Nylon 12CF Flat (XY) sample.

TMA

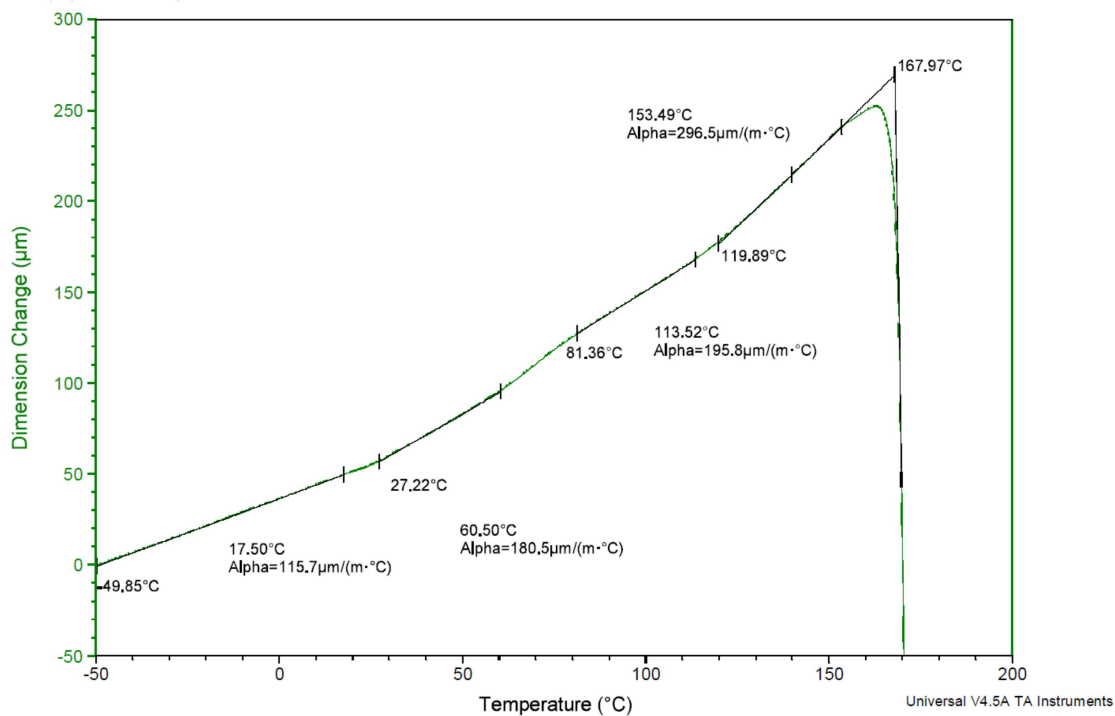


Figure 3. Dimension change data as a function of temperature for the Nylon 12CF On Edge (XZ) sample.

TMA


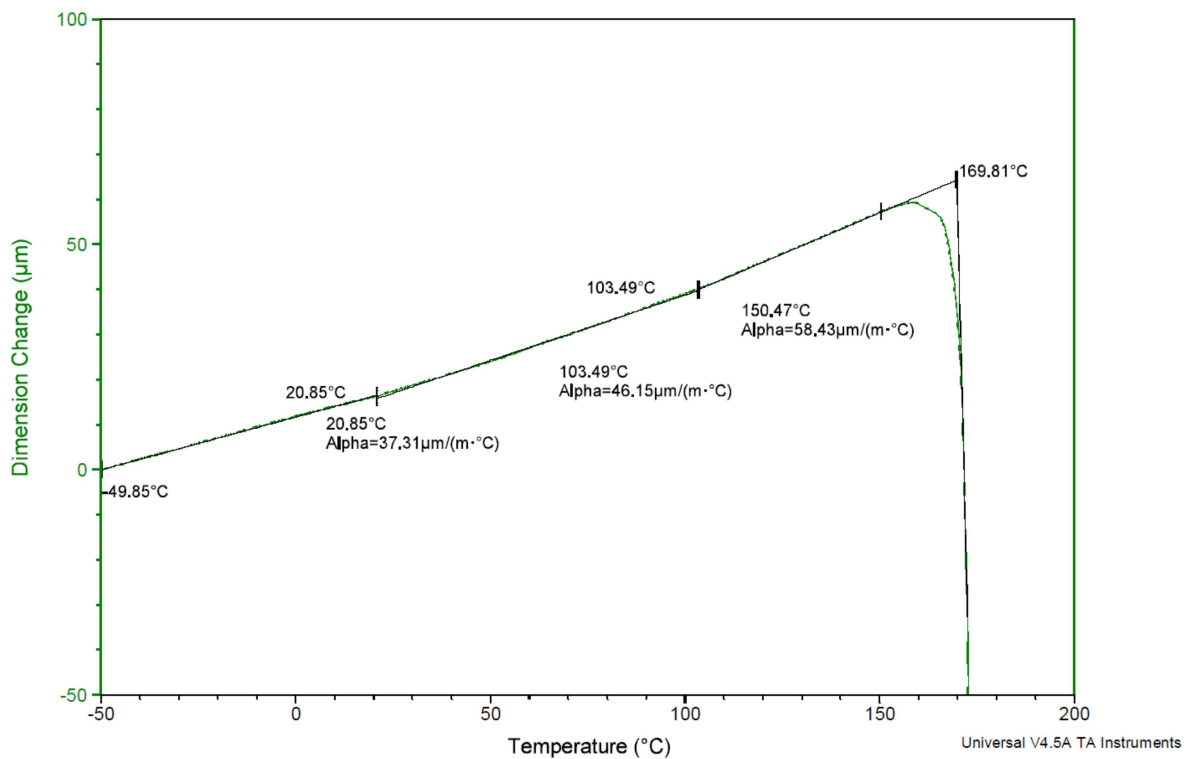


Figure 4. Overlay of the dimension change data for the Flat (XY) and On Edge (XZ) Nylon 12CF samples.

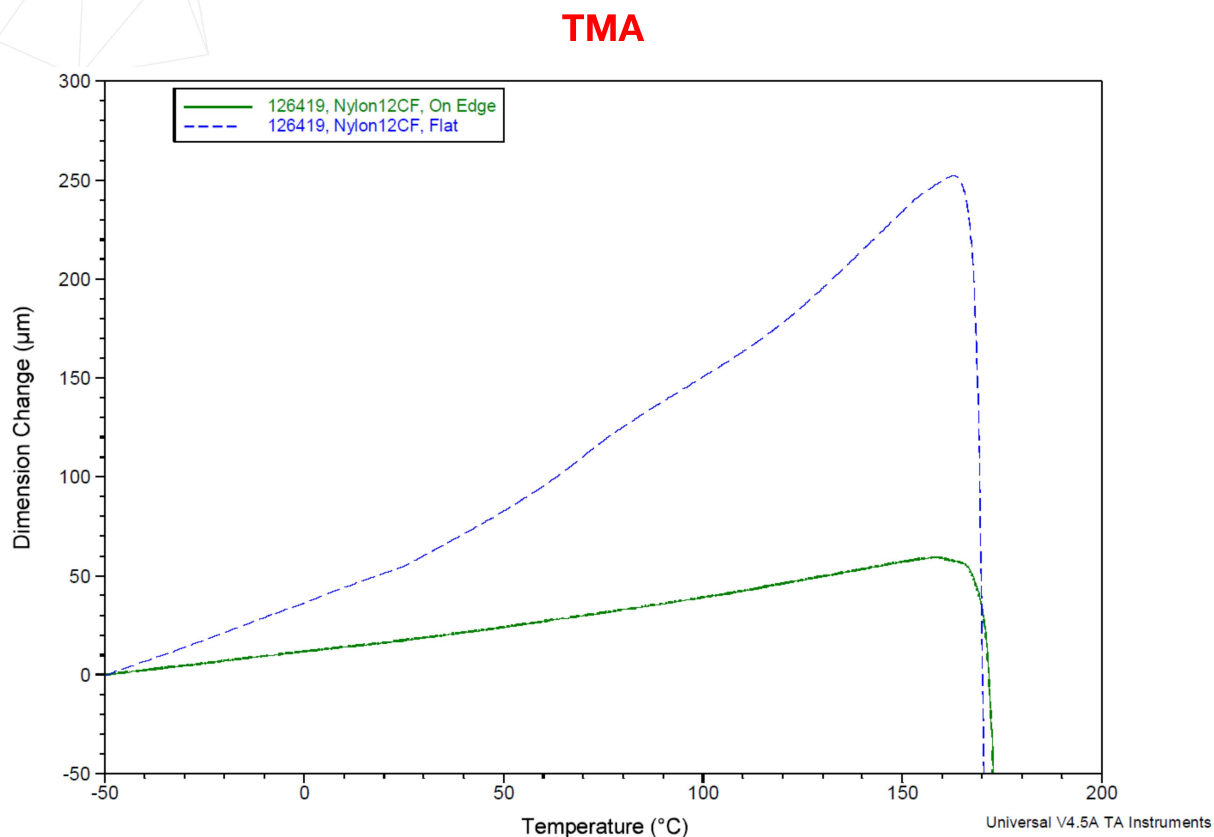

laserlines
 01295 672500
 3dworld@laserlines.co.uk
 www.3dprinting.co.uk

Stratasys Headquarters

7665 Commerce Way,
 Eden Prairie, MN 55344
 +1 800 801 6491 (US Toll Free)
 +1 952 937-3000 (Intl)
 +1 952 937-0070 (Fax)

1 Holtzman St., Science Park,
 PO Box 2496
 Rehovot 76124, Israel
 +972 74 745 4000
 +972 74 745 5000 (Fax)

stratasys.com
 ISO 9001:2015 Certified

© 2020 Stratasys. All rights reserved. Stratasys, the Stratasys Signet logo, FDM, and Fortus are registered trademarks of Stratasys Inc. FDM Nylon 12CF, SR-110, Fortus 380mc CFE, Fortus 450mc and F900 are trademarks of Stratasys, Inc. All other trademarks are the property of their respective owners, and Stratasys assumes no responsibility with regard to the selection, performance, or use of these non-Stratasys products. Product specifications subject to change without notice.
 Printed in the USA. MDS_FDM_Nylon 12CF_0420a

