



# AXXIS®

## Environmental Product Declaration

IN ACCORDANCE WITH ISO 14025:2006  
AND EN 15804:2012+A2:2019/AC:2021

**AXXIS® 0.75mm from New Zealand Steel via EAF**



Programme: **The International EPD System** | [environdec.com](https://www.environdec.com)

Programme Operator: **EPD International AB**

Licensee: **EPD Australasia** | [epd-australasia.com](https://www.epd-australasia.com)

Type of EPD: **EPD of a single product from a manufacturer, from a single site**

EPD Registration number: **EPD-IES-0022703:001**

Version date: **2026-05-31**

Validity date: **2031-05-31**

**This product is not yet on the market – Results of this EPD shall be used with care as the LCI data for this product is not yet based on 1 year of production which may result in increased uncertainty.**

An EPD may be updated or depublished if conditions change.  
To find the latest version of the EPD and to confirm its validity,  
see [www.environdec.com](https://www.environdec.com).



Environmental Product Declaration

AXXIS® 0.75mm from New Zealand Steel

Information about EPD Owner

New Zealand Steel's (NZS) Glenbrook mill, located about 60 km south of Auckland, is a fully integrated steel plant that produces flat rolled steel products. It's unique in that it uses locally sourced ironsand as its ore and is the sole producer of such products in New Zealand. The mill produces around 670,000 tonnes of steel annually, which is used in various sectors including building, construction, manufacturing, and agriculture.

The NZS site holds AS/NZS ISO 9001 "Quality Management System" and AS/NZS ISO 14001 "Environmental Management System" certifications. Its various steel products also achieve Eco Choice certifications; Flat and Long Steel Products EC-41-15 and Pre-Painted Steel Products EC-57.



Manufacturing & Processing in New Zealand

New Zealand Steel is in the process of installing an electric arc furnace (EAF) which will replace the current oxygen based steelmaking process via the Klockner Oxygen Blown Maxhutte (KOBM). This marks a significant decarbonisation step change in the steelmaking process by enabling large scale incorporation of external scrap, replacing a significant amount of primary iron requirements. This EPD reflects the significance of this upcoming change, and the need to produce this specific EPD for product not yet on the market.

The EAF started commissioning in late 2025, and is planned to be fully operational in 2026. This change is expected to reduce site emissions by up to 1Mt of CO<sub>2</sub> annually (RNZ, 2024). All steel will be produced via the EAF, which can accept a combination of molten pig iron (produced from iron sand) or secondary steel scrap (post-industrial/post-consumer). This will also enable the production of very low emissions steel made with 100% scrap at the EAF.

New Zealand Steel manufactures steel from raw and recycled materials using an 'integrated steelmaking' method. This involves the use of ironsand, coal, steel scrap, fluxes (limestone) and alloying materials to produce steel slab via multi hearth, rotary kilns, melters, KOBM steelmaking and continuous slab casting, prior to hot rolling, cold rolling, metal coating and painting.

| Information about EPD Owner |                                                                                                                                                                                                                                                                                     |                                                                                       |
|-----------------------------|-------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------|---------------------------------------------------------------------------------------|
| Declaration Owner:          | <p><b>New Zealand Steel</b><br/>Web: <a href="http://www.nzsteel.co.nz">www.nzsteel.co.nz</a><br/>Email: <a href="mailto:info@nzsteel.co.nz">info@nzsteel.co.nz</a><br/>Phone: 0800 697 833<br/>Post: Private Bag 92121, Auckland 1142, New Zealand</p>                             |  |
| Life Cycle Assessment (LCA) |                                                                                                                                                                                                                                                                                     |                                                                                       |
| LCA Accountability:         | <p>thinkstep Ltd<br/>Barbara Nebel<br/>Gaya Gamage<br/>Web: <a href="http://www.thinkstep-anz.com">www.thinkstep-anz.com</a><br/>Email: <a href="mailto:info@thinkstep-anz.com">info@thinkstep-anz.com</a><br/>Post: 11 Rawhiti Road, Pukerua Bay, Wellington 5026, New Zealand</p> |  |
| Geographical Scope:         | New Zealand                                                                                                                                                                                                                                                                         |                                                                                       |
| Reference Year for Data:    | 2023-07-01 to 2024-06-30                                                                                                                                                                                                                                                            |                                                                                       |
| Version History:            | 001 (2026-05-31) Original version of the EPD                                                                                                                                                                                                                                        |                                                                                       |

## Product Information

### Product covered by EPD

AXXIS® steel is a metallic coated steel product designed to be fabricated into light gauge steel framing for use in residential and commercial structural applications.

This EPD sets out information on the average AXXIS® steel product manufactured by New Zealand Steel, in a base metal thickness of 0.75mm.

AXXIS® steel products represented in this EPD consist of a steel substrate that is coated with a galvanised metallic coating class of Z275, providing enhanced corrosion resistance. AXXIS® steel can be easily identified by its blue surface treatment.

The base steel strength grades G500 or G550, conform to AS 1397:2021 Continuous Hot-dip Metallic Coated Steel Sheet and Strip - Coatings of Zinc and Zinc Alloyed with Aluminium and Magnesium.

For more information, please contact New Zealand Steel at <https://www.nzsteel.co.nz/contact-us/>.



Table 1: Product Description and characteristics

| Product      | Steel category                                                   | Key characteristics                                                                                                                                                                                                                                                                                                                                                                                              |
|--------------|------------------------------------------------------------------|------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------|
| AXXIS® Steel | AXXIS® steel is designed for New Zealand's house-framing market. | <ul style="list-style-type: none"><li>– Metal coating is zinc, Z275</li><li>– AS 1397: Continuous hot-dip metallic coated steel sheet and strip - Coatings of zinc and zinc alloyed with aluminium and magnesium</li><li>– Dimensional tolerance to AS1365 Tolerances for flat-rolled steel products</li><li>– NASH Standard Part 2:2019 Light Steel Framed Buildings</li><li>– Blue surface treatment</li></ul> |

Table 2: Industry Classification

| Product      | Classification | Code | Category                     |
|--------------|----------------|------|------------------------------|
| AXXIS® Steel | UN CPC Ver.2   | 412  | Products of iron or steel    |
|              | ANZSIC 2006    | 2711 | Iron and Steel Manufacturing |

This product is not yet on the market – Results of this EPD shall be used with care as the LCI data for this product is not yet based on 1 year of production which may result in increased uncertainty.

# Electric Arc Furnace - The Future of Steelmaking

The Electric Arc Furnace (EAF) helps secure the future of steelmaking at the Glenbrook site in Auckland. It will enable New Zealand Steel to shrink its carbon footprint and will enable New Zealand, to be as close to self-sufficient as possible, utilising a largely renewable grid and recycling scrap steel.

In a landmark partnership between New Zealand Steel and the Government, the Electric Arc Furnace (EAF) project at the Glenbrook steel works, South of Auckland, replaces the current oxygen steelmaking furnace and decommissioning of two coal-fuelled kilns, achieving a substantial cut in coal use and carbon emissions.

Using an average of 30 megawatts on New Zealand's largely renewable grid, the EAF will melt down steel scrap, previously exported offshore, and process it into prime steel for new products. This initiative will provide our customers with lower carbon steel products, helping them build a stronger and more sustainable New Zealand.

## Same steel, lower emissions

The EAF started commissioning in late 2025, with products expected to become available in market in 2026. To support this monumental change and give certainty, we are working with Thinkstep to develop a new range of environmental product declarations (EPDs), for both NZ Steel & Pacific Steel products. For updates visit [www.nzsteel.co.nz/sustainability/](http://www.nzsteel.co.nz/sustainability/) or reach out to [sustainability@nz.bluescopesteel.com](mailto:sustainability@nz.bluescopesteel.com) for more information.

The feed source of the EAF will be a standard blend of 50-60% scrap with a balance of liquid iron, significantly reducing the embodied carbon of all our steel products. We are also developing a new, much lower embodied carbon steel product, made from 100% scrap, (majority from post-consumer and post-industrial sources, with some home scrap).


## The future is circular

The EAF project exemplifies the benefits of a local circular economy model for both our industry and country. It enables us to solidify the circularity of steel, with the EAF allowing the recycling and manufacturing of steel within New Zealand in a continuous loop.


## Our unique process, upgraded

### The Electric Arc Furnace Process

Compared to the standard process, half the kilns and melter are required and external scrap can now be used.

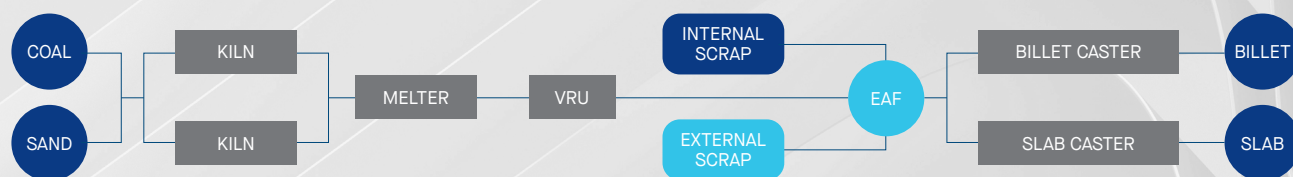

### The Original Process

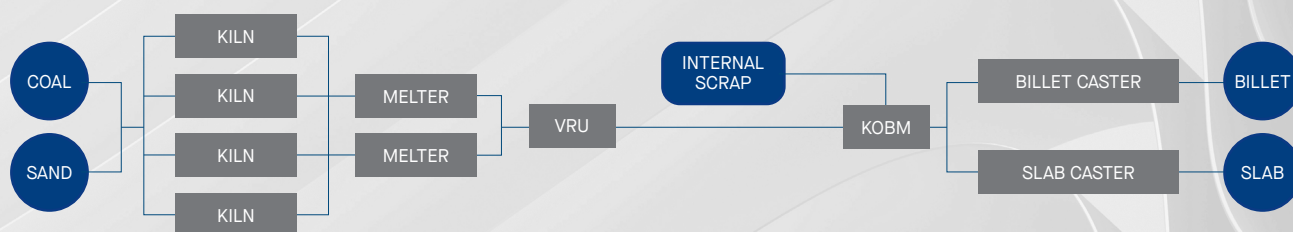

## Content Declaration

The typical steel composition, product content and packaging for 1m<sup>2</sup> of AXXIS® 0.75mm is given below.

**Table 3: Typical steel composition for 1 kg of carbon steel**

| Components   | Mass (kg)   |
|--------------|-------------|
| Iron         | >0.97       |
| Manganese    | <0.008      |
| Silicon      | <0.005      |
| Chromium     | <0.001      |
| Carbon       | <0.001      |
| Other        | <0.001 each |
| <b>TOTAL</b> | <b>1</b>    |

**Table 4: Content declaration for 1m<sup>2</sup> AXXIS® 0.75mm via EAF**

| Product Composition | Material           | Mass (kg)   | Post-consumer recycled material, mass-% of product* | Biogenic material, mass-% of product | Biogenic material, kg C/declared unit |
|---------------------|--------------------|-------------|-----------------------------------------------------|--------------------------------------|---------------------------------------|
| Steel Substrate     | Carbon steel       | 5.89        | 42.2%                                               | 0                                    | 0                                     |
| Metal Coating       | Zinc coating, Z275 | 0.297       | 0                                                   | 0                                    | 0                                     |
| <b>TOTAL</b>        |                    | <b>6.18</b> | <b>42.2%</b>                                        | <b>0</b>                             | <b>0</b>                              |

\*External scrap inputs include shred and heavy metal scrap (HMS), both of which are largely made up of post-consumer scrap. NZ Steel experts calculate post-consumer recycled material content based on estimates of available shred and HMS. This product consists of the standard blend of 50-60% scrap with a balance of liquid iron.

**Table 5: Content declaration of Packaging for 1m<sup>2</sup> AXXIS® 0.75mm via EAF**

| Packaging Materials | Mass (kg)       | Mass-% (versus the product) | Biogenic material, kg C/declared unit |
|---------------------|-----------------|-----------------------------|---------------------------------------|
| Plastic film        | 1.20E-02        | 0.19%                       | 0                                     |
| Paper               | 4.63E-04        | 0.01%                       | 2.08E-04                              |
| Steel               | 5.63E-05        | 0.00%                       | 0                                     |
| HDPE                | 3.16E-03        | 0.05%                       | 0                                     |
| Timber              | 3.56E-03        | 0.06%                       | 1.49E-03                              |
| <b>TOTAL</b>        | <b>1.92E-02</b> | <b>0.31%</b>                | <b>1.70E-03</b>                       |

## Dangerous substances from the candidate list of SVHC for Authorisation

The product declared within this EPD:

- Does not release dangerous substances to soil and water
- Does not contain hazardous substances requiring labelling
- Does not contain materials identified in the European Chemicals Agency's Candidate List of Substances of Very High Concern in the products at a concentration greater than 0.1% (ECHA, 2025).

# Life Cycle Assessment (LCA) Information

## Declared Unit

The declared unit presented is 1m<sup>2</sup> of flat AXXIS® 0.75mm product.

**Table 6: Conversion to mass**

| Product              | Metallic Coating | Base Metal Thickness (mm) | Product Mass (kg/m <sup>2</sup> flat product) |
|----------------------|------------------|---------------------------|-----------------------------------------------|
| <b>AXXIS® 0.75mm</b> | Z275             | 0.75                      | 6.18                                          |

## System boundaries


As shown in the table below, this EPD is of the type Cradle to gate with modules C1–C4 and module D (A1–A3 + C + D). Other life cycle stages (Modules A4-A5, B1-B7) are dependent on particular scenarios and best modelled at the building level.

**Table 7: Modules included in the scope of the EPD**

|                         | Product stage       |                            |               | Distribution/<br>installation stage |                             | Use stage |             |        |             |               |                        |                       | End-of-life stage           |                               |                  |          | Beyond product life cycle              |
|-------------------------|---------------------|----------------------------|---------------|-------------------------------------|-----------------------------|-----------|-------------|--------|-------------|---------------|------------------------|-----------------------|-----------------------------|-------------------------------|------------------|----------|----------------------------------------|
|                         | Raw material supply | Transport of raw materials | Manufacturing | Transport to customer               | Construction / installation | Use       | Maintenance | Repair | Replacement | Refurbishment | Operational energy use | Operational water use | De-construction, demolition | Transport to waste processing | Waste processing | Disposal | Reuse / recovery / recycling potential |
| <b>Module</b>           | A1                  | A2                         | A3            | A4                                  | A5                          | B1        | B2          | B3     | B4          | B5            | B6                     | B7                    | C1                          | C2                            | C3               | C4       | D                                      |
| <b>Modules declared</b> | X                   | X                          | X             | ND                                  | ND                          | ND        | ND          | ND     | ND          | ND            | ND                     | ND                    | X                           | X                             | X                | X        | X                                      |
| <b>Geography</b>        | GLO                 | GLO                        | NZ            |                                     |                             |           |             |        |             |               |                        |                       | NZ                          | NZ                            | NZ               | NZ       | GLO                                    |


X = included in the EPD; ND = Module not declared (such a declaration shall not be regarded as an indicator result of zero)

## Product system process flow diagram

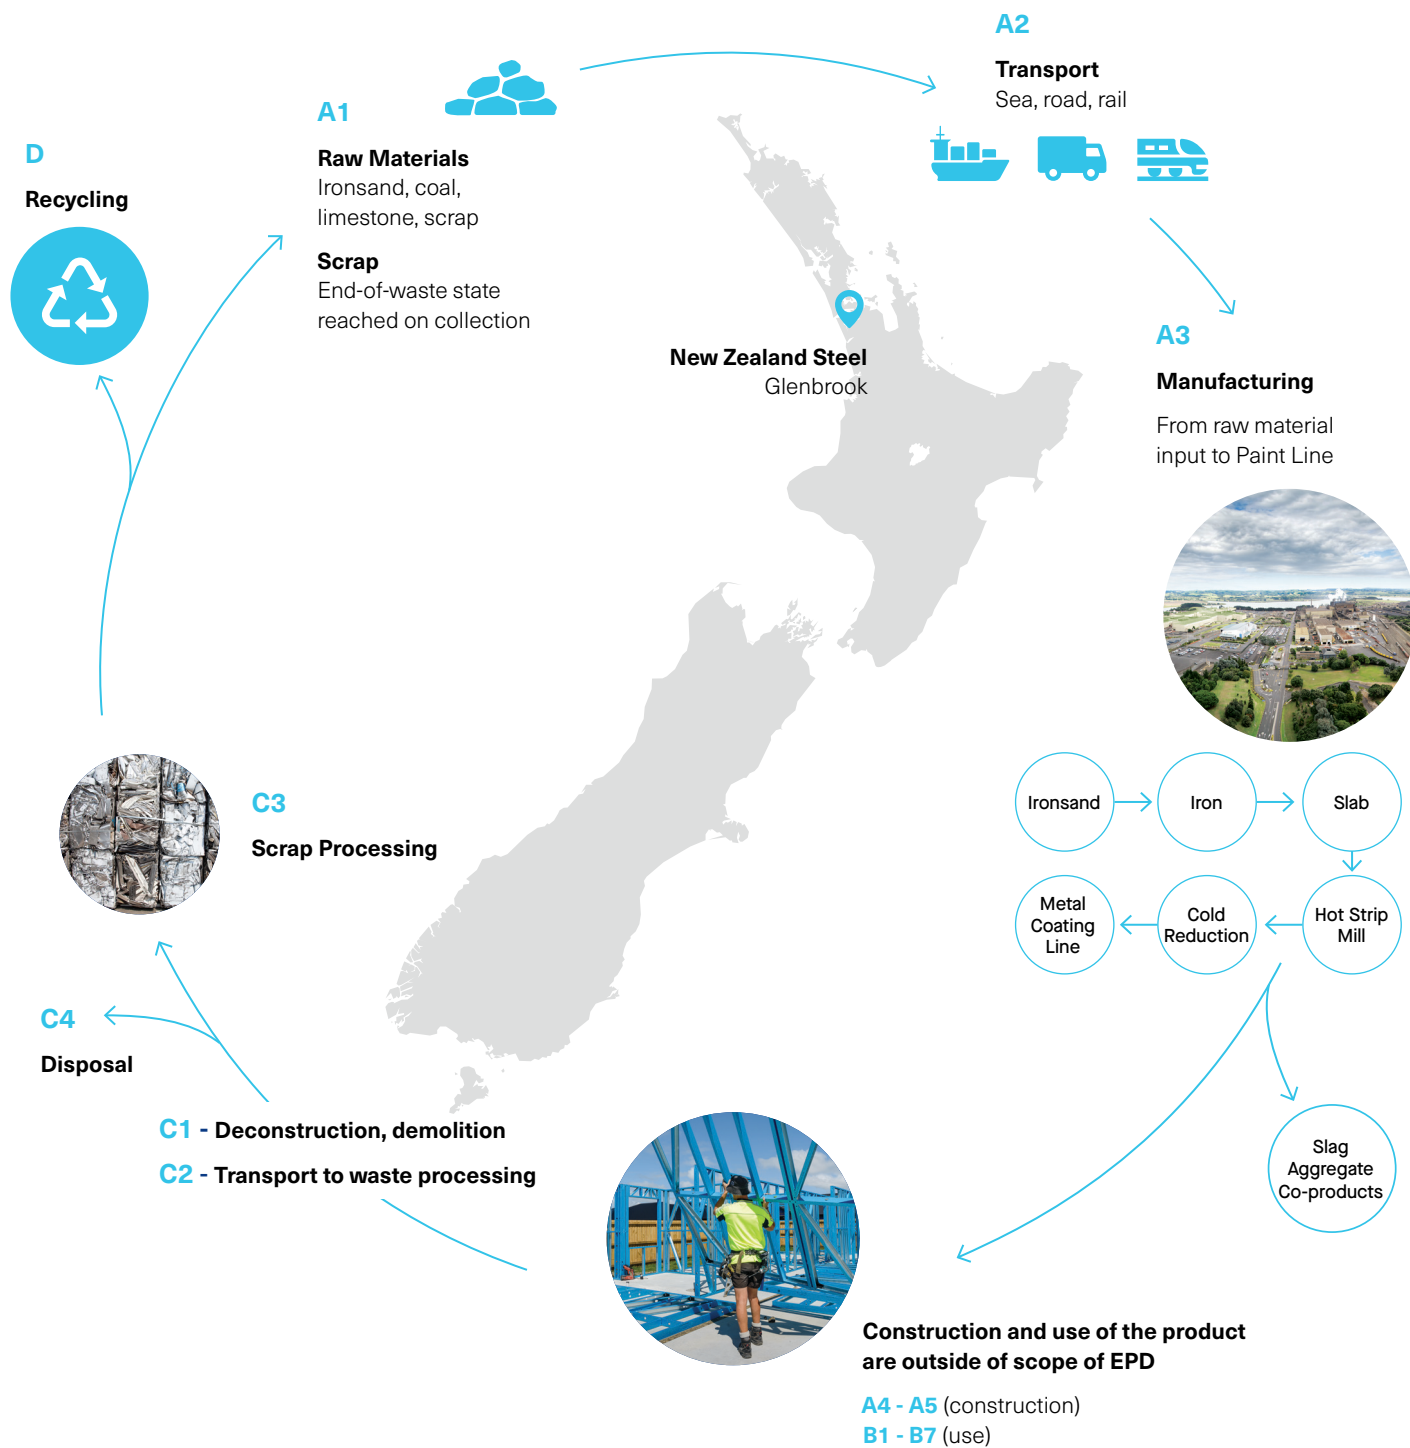

## A1 - A3 Manufacturing Process

### A1 – RAW MATERIALS



IRONSAND



COAL




LIME



STEEL SCRAP (FOR EAF)  
(End-of-waste state reached on collection)

### A2 – TRANSPORT



### A3 – MANUFACTURING




INPUT: ENERGY & WATER

#### IRONMAKING



MHF



KILNS




MELTER


#### STEELMAKING



SCRAP STEEL




EAF



SLAB CASTING


#### HOT ROLLING MILL

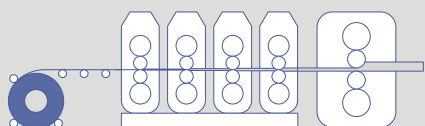


#### GAS REHEAT FURNACE




#### STEEL SLAB YARD



#### COLD ROLLING MILL



#### METAL COAT LINE

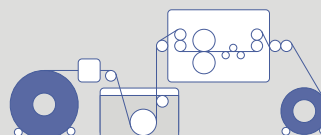

### OUTPUTS



SLAG AGGREGATE CO-PRODUCTS,  
WASTE, EMISSIONS, WASTEWATER



FINISHED PRODUCT

# Environmental Product Declaration

## AXXIS® 0.75mm from New Zealand Steel

---

### Life Cycle Assessment (LCA) Methodology

The underlying LCA model was developed using the Life Cycle for Experts (LCA FE) software version 10.9 (formerly known as GaBi Software) for life cycle engineering, developed by Sphera Solutions, Inc.

Data for all energy inputs, transport processes and raw materials are from the Managed LCA Content (MLC) Database 2024.2 (Sphera, 2024). Most datasets have a reference year between 2020 and 2023, and therefore, all datasets are within the 10-year limit allowable for generic/secondary data under EN 15804 and the PCR.

#### Electricity

Electricity for primary iron making was based on New Zealand Steel's cogeneration plants. Steel making (EAF) and downstream processes use purchased electricity. New Zealand Steel does not purchase specific electricity mixes that provide Guarantee of Origin. Therefore, the residual electricity mix on the market is used for A1 and A3 processes that NZ Steel has control over.

The composition of the residual electricity grid mix of New Zealand is modelled in LCA FE 2024.2 based on published data for the year 1st April 2021 – 31st March 2022 (BraveTrace, 2023). The New Zealand residual electricity mix is made up of hydro (56.6%), geothermal (19.7%) natural gas (12.5%), wind (6.55%), coal (4.25%), biomass (0.266%) and biogas (0.160%). Onsite consumption (3.00%), and the medium voltage (1kV-60kV) grid's transmission and distribution losses (3.17%) are calculated based on data from the Ministry of Business, Innovation & Employment (MBIE, 2023). The emission factor for the New Zealand residual grid mix for the GWP-GHG indicator is 0.146 kgCO<sub>2</sub>e/kWh (based on EF3.1).

Location-based grid mix is used for other electricity consumption including Modules C and D. The emission factor for the New Zealand location-based grid mix for the GWP-GHG indicator is 0.143 kg CO<sub>2</sub>e/kWh (based on EF3.1).

#### Modelling of infrastructure/capital goods

Capital goods and infrastructure associated with electricity have been included in the background datasets as provided by the Managed LCA Content (MLC) database (Sphera, 2024). Infrastructure/capital goods associated with all other upstream, core and downstream processes have been excluded.

### Allocation

Life cycle inventory data was provided specifically per process. For the iron making stage, economic allocation is applied to processes where slags produced are sold. Allocation was not required for other processes such as mining. Cut-off approach is applied for slag produced at the EAF. Steel scrap outputs during production are internally recycled at NZ Steel's EAF.

Sub-metered electricity usage was available per process (e.g., for iron making, steel making, hot strip milling). Where submetering did not exist, electricity is allocated based on output mass.

For metal coating, relevant physical quantities, predominantly the mass of throughput (e.g. steel coil) or surface area of the coil (e.g. surface coatings) are used in allocation. For example, zinc is allocated based on the quantities required for coating a specific area to a selected coating thickness.

The packaging materials are allocated by mass across the total output of packaged products.

#### Recycling and recycled inputs

The model assumes that 42.2% of steel slab used to make this product is produced from post-consumer scrap, 4% post-industrial scrap and the remaining 52% from primary iron.

Internal steel scrap from production is treated as an internal flow that does not require allocation. Internally recycled scrap at NZ Steel's EAF is modelled burden-free. The internal scrap is made up of scrap containing iron, post-industrial and post-consumer scrap.

Post-industrial scrap has a burden based on assumed economic allocation between product and scrap. This was calculated using the price ratio between welded beams/columns produced from steel plate and the steel scrap generated from this process. GWP-GHG impact of post-industrial scrap is 0.302 kg CO<sub>2</sub> eq. per kg of steel scrap. This is likely a conservative value, as the relative value of welded beams/columns is not as high as for steel products that have undergone further processing. The impact of the allocation of post-industrial scrap on the LCA results depends on the percentage of post-industrial scrap input. For this EPD, impact from post-industrial scrap is immaterial.

Post-consumer scrap is considered burden-free at the end-of-waste point, after which it incurs the impacts of shredding and transport to the EAF. The GWP-GHG of post-consumer scrap is 0.0158 kg CO<sub>2</sub> eq per kg of steel scrap delivered to NZ Steel.

## Data Quality Assessment

A data quality assessment that complies with EN 15941 (CEN, 2024) was done as part of the LCA study.

**Table 8: Data sources and share of primary data**

| Process                                                                          | Source type                 | Source      | Reference year | Data category | Share of primary data, of GWP-GHG results for A1-A3 |
|----------------------------------------------------------------------------------|-----------------------------|-------------|----------------|---------------|-----------------------------------------------------|
| Process emissions from manufacturing (from mining to painted product)            | Collected data and database | EPD owner   | 2019-2023      | Primary       | 67.6%                                               |
| Natural gas used in the manufacturing process (from mining to painted product)   | Collected data and database | EPD owner   | 2024           | Primary       | 8.5%                                                |
| Other fuels used in the manufacturing process (from mining to painted product)   | Collected data and database | EPD owner   | 2024           | Primary       | 0.4%                                                |
| Electricity used in the manufacturing process (from mining to painted product)   | Collected data and database | MLC v2024.1 | 2024           | Primary       | 4.8%                                                |
| Raw materials used in the manufacturing process (from mining to painted product) | Collected data and database | MLC v2024.1 | 2024           | Secondary     | 0.0%                                                |
| Transport of raw materials to site                                               | Collected data and database | MLC v2024.1 | 2024           | Primary       | 0.2%                                                |
| Other processes                                                                  | Database                    | MLC v2024.1 | 2019-2023      | Secondary     | 0.0%                                                |
| Packaging                                                                        | Database                    | MLC v2024.1 | 2019-2023      | Secondary     | 0.0%                                                |
| <b>TOTAL SHARE OF PRIMARY DATA*, OF GWP-GHG RESULTS FOR A1-A3</b>                |                             |             |                |               | <b>81.4%</b>                                        |

\* The share of primary data is calculated based on GWP-GHG results. It is a simplified indicator for data quality that supports the use of more primary data, to increase the representativeness of and comparability between EPDs. Note that the indicator does not capture all relevant aspects of data quality and is not comparable across product categories.

### Time, geographical and technical representativeness

New Zealand Steel's Life Cycle Inventory (LCI) is based on a mix of data periods. All critical processes (i.e. processes with high contribution to environmental impact) are based on data from 2023-07-01 to 2024-06-30. Other processes (minimal contribution to environmental impact) reflect data for the period from 2018-07-01 to 2019-06-30. These processes have not seen process changes over the years and remain valid.

Data for the EAF is theoretical, based on engineering calculations. Data on scrap inputs (post-industrial and post-consumer) are theoretical, based on estimates made by experts. The quality of data used for modelling the EAF (both specific and generic data as per EN15941) is fair. Data used for other processes are either good or very good. No poor or very poor data is used. The use of fair data with more than 30% impact contribution to any core indicator is disclosed in Table 9.

All specific data (e.g., inbound transport, mining, ironmaking, and steelmaking) comes from New Zealand Steel, sourced from the Waikato North Head mine in Waikato and the Glenbrook Steelworks in Glenbrook, Auckland, New Zealand. Production and end-of-life stages are modelled for New Zealand. The default factors from the PCR are used to model module C. International datasets have been used for inputs purchased internationally or where location specific datasets were unavailable. Data taken from the MLC database reflects average or generic production and therefore does not correspond to actual New Zealand Steel suppliers.

Since this is an EPD for products not yet on the market, an updated EPD will be produced once specific data are available.

# Environmental Product Declaration

## AXXIS® 0.75mm from New Zealand Steel

Table 9: Data quality information for AXXIS® 0.75mm

| Data set   | Criteria and data quality level | Reason for level                 | Reason for using    | Relevance                                                                                   |
|------------|---------------------------------|----------------------------------|---------------------|---------------------------------------------------------------------------------------------|
| Zinc       | Geographical - Fair             | Proxy or generic background data | Best available data | 99% of ADP-minerals&metals;<br>58% of EP-freshwater<br>0-9% of other core impact indicators |
|            | Technical - Fair                |                                  |                     |                                                                                             |
| Electrodes | Geographical - Fair             |                                  |                     | 99% of ODP<br>0-4% of other core impact indicators                                          |
|            | Technical - Fair                |                                  |                     |                                                                                             |

## Modelling beyond A1-A3

The processes below are included in the product system to be studied. For modules beyond A3, the scenarios included are currently in use and are representative for one of the most probable alternatives.

### End of Life (Modules C1-C4)

The recycling scenario in this EPD was based on a steel recycling report for New Zealand Heavy Engineering Research Association (HERA), where it was estimated that 85% of steel scrap from the building and infrastructure sector is recovered (thinkstep-anz, 2021). This is used for all products in this EPD and is considered conservative. Results for 100% landfill and 100% recycling are provided as per PCR 2019:14.

End-of-life Modules (C1 – C4) were modelled based on default data from PCR 2019:14 (EPD International, 2025b). End-of-life allocation follows the requirements of EN15804:2012+A2:2019 (CEN, 2021) section 6.4.3.3.

Table 10: End-of-Life scenarios for products

| Process                                                   | Unit                                                                                                                                                                                                                                                                                                                                                                                                                 |                         |                           |
|-----------------------------------------------------------|----------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------|-------------------------|---------------------------|
|                                                           | EOL Main Scenario                                                                                                                                                                                                                                                                                                                                                                                                    | 100% Recycling Scenario | 100% Landfilling Scenario |
| Collection process specified by type                      | 1 m² of product collected with mixed construction waste                                                                                                                                                                                                                                                                                                                                                              |                         |                           |
| Recovery system specified by type                         | 85% for recycling                                                                                                                                                                                                                                                                                                                                                                                                    | 100%                    | 0%                        |
| Disposal specified by type                                | 15% for landfilling                                                                                                                                                                                                                                                                                                                                                                                                  | 0%                      | 100%                      |
| Assumptions for scenario development, e.g. transportation | C1 - Demolition/deconstruction of steel –diesel use of 1.1 kWh/tonne<br>C2 - 80 km of transport by truck<br>C3 - Loading and unloading at sorting facility (diesel use of 1.8 kWh/tonne); Fragging of steel (diesel use of 7.4 kWh/tonne); Mechanical sorting (electricity use of 2.2 kWh/tonne).<br>C4 - Compacting of inert construction waste for landfills (including backfilling) (diesel use of 1.6 kWh/tonne) |                         |                           |

### Recovery and Recycling potential (Module D)

Module D accounts for the net environmental benefits or burdens - beyond the system boundary - resulting from the recycling of scrap. It only applies to the net flow of recyclable materials, meaning that any potential benefits are calculated after deducting the post-consumer scrap used as input in the product's life cycle from the amount of scrap made available for recycling at the end-of-life.

Module D impacts are modelled using a combination of industry average inventories (45%) (worldsteel value of scrap dataset (Sphera, 2024)) and NZ Steel value of scrap (55%). The steel value of scrap datasets represents the difference between impact when manufacturing 100% primary and 100% secondary steel, and is used to represent the credit/burden at module D.

Module D for this EPD results in a credit as there is more net scrap available than scrap input required. The net flow is calculated as 5.00 kg of scrap out minus 3.49 kg of scrap in, resulting in a net flow of 1.52 kg out per m² of AXXIS®. The input of secondary material needed for the production of steel is calculated based on gross inputs, which is 1.2 kg EAF steel per kg of steel substrate.

# Environmental Product Declaration

## AXXIS® 0.75mm from New Zealand Steel

---

### Cut off criteria

The cut-off criteria applied are: 1% of renewable and non-renewable primary energy usage, 1% of the total mass input of a process and 1% of environmental impacts.

Transport and packaging of minor raw materials that are insignificant to the overall impacts have been cut off.

### Key assumptions

- Data for the EAF was based on modelled data provided by NZ Steel and the EAF designers, as this EPD relates to a product not yet on the market and the EAF was not operational at the time of publication. Similarly, the % scrap input is based on modelling and estimation of scrap forecasts.
- The split of scrap recycled domestically and internationally reflect NZ Steel's expected total demand of New Zealand's total scrap production. However, since steel scrap is a global commodity and now domestically sought for the EAF, the split and results may not be fully representative for NZ Steel.
- Any wastes from the production process (Module A3) are assumed to be transported over a 100 km distance to a treatment or disposal site.
- Where specific life cycle inventory data were unavailable, proxy data were used, giving preference to regional data.

### Assessment Indicators

The results tables describe the different environmental indicators for each product per declared unit, for each declared module. The EN 15804 reference package based on EF 3.1 is used.

- Table 11 contains the core environmental impact indicators in accordance with EN 15804:2012+A2:2019 (CEN, 2021), describing the potential environmental impacts of the product.
- Table 12 provides additional environmental impact indicators in accordance with EN 15804:2012+A2:2019 (CEN, 2021).
- Table 13 shows the life cycle inventory indicators for resource use.
- Table 14 displays the life cycle inventory indicators for waste and other outputs.
- Table 15 displays biogenic carbon content indicators.
- Table 16 contains results for environmental impact indicators in accordance with EN 15804:2012+A1:2013 (CEN, 2013) to aid backward comparability.

The estimated impact results are only relative statements, which do not indicate the endpoints of the impact categories, exceeding threshold values, safety margins and/or risks.

The use of primary energy is separated into energy used as raw material and energy used as energy carrier as per option C in Annex 3 in the PCR (EPD International, 2025b).

Energy indicators (MJ) are always given as net calorific value.

# Environmental Product Declaration

AXXIS® 0.75mm from New Zealand Steel

**Table 11: EN15804+A2 Core Environmental Impact Indicators**

| Impact category                                                   | Indicator           | Unit                        |
|-------------------------------------------------------------------|---------------------|-----------------------------|
| Climate change – total                                            | GWP-total           | kg CO <sub>2</sub> -eq.     |
| Climate change – fossil                                           | GWP-fossil          | kg CO <sub>2</sub> -eq.     |
| Climate change – biogenic                                         | GWP-biogenic        | kg CO <sub>2</sub> -eq.     |
| Climate change – land use and land use change                     | GWP-luluc           | kg CO <sub>2</sub> -eq.     |
| Ozone depletion                                                   | ODP                 | kg CFC11-eq.                |
| Acidification                                                     | AP                  | Mole of H <sup>+</sup> eq.  |
| Eutrophication aquatic freshwater                                 | EP-freshwater       | kg P eq.                    |
| Eutrophication aquatic marine                                     | EP-marine           | kg N eq.                    |
| Eutrophication terrestrial                                        | EP-terrestrial      | Mole of N eq.               |
| Photochemical ozone formation                                     | POCP                | kg NMVOC eq.                |
| Depletion of abiotic resources – minerals and metals <sup>1</sup> | ADP-minerals&metals | kg Sb-eq.                   |
| Depletion of abiotic resources – fossil fuels <sup>1</sup>        | ADP-fossil          | MJ                          |
| Water use <sup>1</sup>                                            | WDP                 | m <sup>3</sup> world equiv. |

**Table 12: EN15804+A2 Additional Environmental Impact Indicators**

| Impact category                                      | Indicator          | Unit                    |
|------------------------------------------------------|--------------------|-------------------------|
| Climate Change <sup>2</sup>                          | GWP-GHG            | kg CO <sub>2</sub> -eq. |
| Climate Change <sup>3</sup>                          | GWP-GHG (IPCC AR5) | kg CO <sub>2</sub> -eq. |
| Particulate Matter emissions                         | PM                 | Disease incidences      |
| Ionising Radiation – human health <sup>4</sup>       | IRP                | kBq U235 eq.            |
| Eco-toxicity (freshwater) <sup>1</sup>               | ETP-fw             | CTUe                    |
| Human Toxicity, cancer <sup>1</sup>                  | HTP-c              | CTUh                    |
| Human Toxicity, non-cancer <sup>1</sup>              | HTP-nc             | CTUh                    |
| Land use related impacts / soil quality <sup>1</sup> | SQP                | Dimensionless (Pt)      |

**Table 13: Life cycle inventory indicators on use of resources**

| Parameter                                                                                                  | Indicator | Unit           |
|------------------------------------------------------------------------------------------------------------|-----------|----------------|
| Use of renewable primary energy excluding renewable primary energy resources used as raw materials         | PERE      | MJ             |
| Use of renewable primary energy resources used as raw materials                                            | PERM      | MJ             |
| Total use of renewable primary energy resources                                                            | PERT      | MJ             |
| Use of non-renewable primary energy excluding non-renewable primary energy resources used as raw materials | PENRE     | MJ             |
| Use of non-renewable primary energy resources used as raw materials                                        | PENRM     | MJ             |
| Total use of non-renewable primary energy resources                                                        | PENRT     | MJ             |
| Use of secondary material                                                                                  | SM        | kg             |
| Use of renewable secondary fuels                                                                           | RSF       | MJ             |
| Use of non-renewable secondary fuels                                                                       | NRSF      | MJ             |
| Net use of fresh water                                                                                     | FW        | m <sup>3</sup> |

# Environmental Product Declaration

AXXIS® 0.75mm from New Zealand Steel

**Table 14: Life cycle inventory indicators on waste categories and output flows**

| Parameter                     | Indicator | Unit |
|-------------------------------|-----------|------|
| Hazardous waste disposed      | HWD       | kg   |
| Non-hazardous waste disposed  | NHWD      | kg   |
| Radioactive waste disposed    | RWD       | kg   |
| Components for reuse          | CRU       | kg   |
| Materials for energy recovery | MER       | kg   |
| Materials for recycling       | MFR       | kg   |
| Exported electrical energy    | EEE       | MJ   |
| Exported thermal energy       | EET       | MJ   |

**Table 15: Biogenic carbon content indicators**

| Parameter                           | Indicator | Unit |
|-------------------------------------|-----------|------|
| Biogenic carbon content - product   | BCC-prod  | kg C |
| Biogenic carbon content - packaging | BCC-pack  | kg C |

Note: 1 kg biogenic carbon is equivalent to 44/12 kg CO<sub>2</sub>

**Table 16: EN15804+A1 Environmental Impact Indicators**

| Impact category                                      | Indicator         | Unit                                  |
|------------------------------------------------------|-------------------|---------------------------------------|
| Global warming potential                             | GWP (EN15804+A1)  | kg CO <sub>2</sub> -eq.               |
| Ozone depletion potential                            | ODP (EN15804+A1)  | kg CFC11-eq.                          |
| Acidification potential                              | AP (EN15804+A1)   | kg SO <sub>2</sub> -eq.               |
| Eutrophication potential                             | EP (EN15804+A1)   | kg PO <sub>4</sub> <sup>3-</sup> -eq. |
| Photochemical ozone creation potential               | POCP (EN15804+A1) | kg Ethene-eq.                         |
| Abiotic depletion potential for non-fossil resources | ADPE (EN15804+A1) | kg Sb-eq.                             |
| Abiotic depletion potential for fossil resources     | ADPF (EN15804+A1) | MJ                                    |

Note: the indicators and characterisation methods are from EN 15804:2012+A1:2013, but other LCA rules (system boundaries, allocation, etc.) are according to EN 15804:2012+A2:2019; i.e., the results of the “A1 indicators” shall not be claimed to be compliant with EN 15804:2012+A1:2013.

## Disclaimers

- 1 The results of this environmental impact indicator shall be used with care as the uncertainties on these results are high or as there is limited experience with the indicator.
- 2 This indicator is identical to GWP-total except that the CF for biogenic CO<sub>2</sub> is set to zero. It has been included in the EPD following the PCR.
- 3 GWP-GHG (IPCC AR5) is an additional GWP100 indicator that is aligned with the Intergovernmental Panel on Climate Change (IPCC) 2013 Fifth Assessment Report (AR5) (IPCC 2013), national greenhouse gas reporting frameworks in Australia and New Zealand and previous versions of the Construction Products PCR (PCR2019:14v1.11). It excludes biogenic carbon and indirect radiative forcing.
- 4 This impact category deals mainly with the eventual impact of low dose ionizing radiation on human health of the nuclear fuel cycle. It does not consider effects due to possible nuclear accidents, occupational exposure nor due to radioactive waste disposal in underground facilities. Potential ionizing radiation from the soil, from radon and some construction materials, is also not measured by this indicator.

## Environmental Product Declaration

AXXIS® 0.75mm from New Zealand Steel

# Environmental Performance

The following tables show the results for one declared unit of AXXIS® 0.75mm.

The estimated impact results are only relative statements, which do not indicate the endpoints of the impact categories, exceeding threshold values, safety margins and/or risks.

Biogenic carbon leaving the product system in module A5 has been balanced out already in modules A1-A3. There is no biogenic carbon in the product, but some biogenic carbon is found in packaging.

The results of the end-of-life stage (modules C1-C4) should be considered when using the results of the product stage (modules A1-A3).

Energy indicators (MJ) are always given as net calorific value.

The use of primary energy is separated into energy used as raw material and energy used as energy carrier as per option C in Annex 3 in the PCR (EPD International, 2025b).

## Results for primary scenario

**Table 17: EN15804+A2 Core environmental impact indicators**

| Indicator               | Unit                        | A1-A3    | C1       | C2       | C3       | C4       | D         |
|-------------------------|-----------------------------|----------|----------|----------|----------|----------|-----------|
| GWP-total               | kg CO <sub>2</sub> -eq.     | 1.31E+01 | 6.70E-03 | 7.05E-02 | 4.97E-02 | 1.46E-03 | -3.14E+00 |
| GWP-fossil              | kg CO <sub>2</sub> -eq.     | 1.31E+01 | 6.70E-03 | 7.05E-02 | 4.97E-02 | 1.46E-03 | -3.14E+00 |
| GWP-biogenic            | kg CO <sub>2</sub> -eq.     | 5.01E-03 | 9.93E-07 | 9.52E-06 | 1.80E-05 | 2.17E-07 | 7.58E-03  |
| GWP-luluc               | kg CO <sub>2</sub> -eq.     | 1.97E-03 | 1.76E-07 | 1.86E-06 | 1.57E-06 | 3.83E-08 | -3.35E-04 |
| ODP                     | kg CFC11-eq.                | 1.68E-09 | 6.70E-16 | 7.11E-15 | 9.06E-15 | 1.46E-16 | 4.69E-11  |
| AP                      | Mole of H+ eq.              | 1.40E-01 | 3.98E-05 | 5.22E-04 | 2.92E-04 | 8.68E-06 | -2.61E-02 |
| EP-freshwater           | kg P eq.                    | 5.12E-06 | 1.03E-09 | 1.09E-08 | 1.42E-08 | 2.25E-10 | -2.77E-07 |
| EP-marine               | kg N eq.                    | 1.88E-02 | 1.96E-05 | 2.64E-04 | 1.41E-04 | 4.27E-06 | -2.52E-03 |
| EP-terrestrial          | Mole of N eq.               | 2.12E-01 | 2.14E-04 | 2.89E-03 | 1.56E-03 | 4.67E-05 | -2.67E-02 |
| POCP                    | kg NMVOC eq.                | 5.60E-02 | 5.27E-05 | 5.30E-04 | 3.80E-04 | 1.15E-05 | -8.27E-03 |
| ADP-m&m <sup>1</sup>    | kg Sb-eq.                   | 4.01E-04 | 8.81E-11 | 9.35E-10 | 8.59E-10 | 1.92E-11 | -6.81E-06 |
| ADP-fossil <sup>1</sup> | MJ                          | 1.67E+02 | 8.85E-02 | 9.38E-01 | 6.52E-01 | 1.93E-02 | -3.62E+01 |
| WDP <sup>1</sup>        | m <sup>3</sup> world equiv. | 2.46E+00 | 2.52E-05 | 2.67E-04 | 2.81E-03 | 5.50E-06 | 1.01E-02  |

**Table 18: EN15804+A2 Additional Environmental Impact Indicators**

| Indicator                       | Unit                    | A1-A3    | C1       | C2       | C3       | C4       | D         |
|---------------------------------|-------------------------|----------|----------|----------|----------|----------|-----------|
| GWP-GHG <sup>2</sup>            | kg CO <sub>2</sub> -eq. | 1.31E+01 | 6.70E-03 | 7.05E-02 | 4.97E-02 | 1.46E-03 | -3.14E+00 |
| GWP-GHG (IPCC AR5) <sup>3</sup> | kg CO <sub>2</sub> -eq. | 1.31E+01 | 6.70E-03 | 7.05E-02 | 4.97E-02 | 1.46E-03 | -3.14E+00 |
| PM                              | Disease incidences      | 9.24E-07 | 7.97E-10 | 2.69E-09 | 5.73E-09 | 1.74E-10 | -8.80E-08 |
| IRP <sup>4</sup>                | kBq U235 eq.            | 8.91E-02 | 1.85E-06 | 1.96E-05 | 1.46E-05 | 4.04E-07 | 2.71E-02  |
| ETP-fw <sup>1</sup>             | CTUe                    | 1.13E+02 | 3.95E-02 | 4.19E-01 | 4.41E-01 | 8.61E-03 | -7.40E-01 |
| HTP-c <sup>1</sup>              | CTUh                    | 1.15E-06 | 6.49E-13 | 6.90E-12 | 5.53E-12 | 1.42E-13 | 4.06E-10  |
| HTP-nc <sup>1</sup>             | CTUh                    | 4.16E-08 | 1.42E-11 | 1.51E-10 | 1.02E-10 | 3.10E-12 | -2.16E-09 |
| SQP <sup>1</sup>                | Pt                      | 2.17E+01 | 1.80E-04 | 1.91E-03 | 1.40E-02 | 3.93E-05 | -3.06E+00 |

# Environmental Product Declaration

AXXIS® 0.75mm from New Zealand Steel

**Table 19: Use of resources**

| Indicator | Unit | A1-A3    | C1       | C2       | C3       | C4       | D         |
|-----------|------|----------|----------|----------|----------|----------|-----------|
| PERE      | MJ   | 5.60E+01 | 3.83E-04 | 4.06E-03 | 9.66E-02 | 8.35E-05 | 4.81E-01  |
| PERM      | MJ   | 0.00E+00 | 0.00E+00 | 0.00E+00 | 0.00E+00 | 0.00E+00 | 0.00E+00  |
| PERT      | MJ   | 5.60E+01 | 3.83E-04 | 4.06E-03 | 9.66E-02 | 8.35E-05 | 4.81E-01  |
| PENRE     | MJ   | 1.67E+02 | 8.85E-02 | 9.38E-01 | 6.52E-01 | 1.93E-02 | -3.62E+01 |
| PENRM     | MJ   | 0.00E+00 | 0.00E+00 | 0.00E+00 | 0.00E+00 | 0.00E+00 | 0.00E+00  |
| PENRT     | MJ   | 1.67E+02 | 8.85E-02 | 9.38E-01 | 6.52E-01 | 1.93E-02 | -3.62E+01 |
| SM        | kg   | 3.49E+00 | 0.00E+00 | 0.00E+00 | 0.00E+00 | 0.00E+00 | 0.00E+00  |
| RSF       | MJ   | 0.00E+00 | 0.00E+00 | 0.00E+00 | 0.00E+00 | 0.00E+00 | 0.00E+00  |
| NRSF      | MJ   | 0.00E+00 | 0.00E+00 | 0.00E+00 | 0.00E+00 | 0.00E+00 | 0.00E+00  |
| FW        | m³   | 1.47E-01 | 5.12E-07 | 5.44E-06 | 1.96E-04 | 1.12E-07 | -1.10E-01 |

**Table 20: Waste production and output flows**

| Indicator | Unit | A1-A3    | C1       | C2       | C3       | C4       | D         |
|-----------|------|----------|----------|----------|----------|----------|-----------|
| HWD       | kg   | 9.45E-08 | 1.42E-12 | 1.51E-11 | 3.25E-11 | 3.11E-13 | -9.81E-08 |
| NHWD      | kg   | 7.07E-01 | 2.17E-06 | 2.30E-05 | 3.06E-05 | 9.28E-01 | 3.81E-03  |
| RWD       | kg   | 8.61E-04 | 1.73E-08 | 1.83E-07 | 1.33E-07 | 3.77E-09 | 6.36E-06  |
| CRU       | kg   | 0.00E+00 | 0.00E+00 | 0.00E+00 | 0.00E+00 | 0.00E+00 | 0.00E+00  |
| MFR       | kg   | 0.00E+00 | 0.00E+00 | 0.00E+00 | 5.26E+00 | 0.00E+00 | 0.00E+00  |
| MER       | kg   | 0.00E+00 | 0.00E+00 | 0.00E+00 | 0.00E+00 | 0.00E+00 | 0.00E+00  |
| EEE       | MJ   | 0.00E+00 | 0.00E+00 | 0.00E+00 | 0.00E+00 | 0.00E+00 | 0.00E+00  |
| EET       | MJ   | 0.00E+00 | 0.00E+00 | 0.00E+00 | 0.00E+00 | 0.00E+00 | 0.00E+00  |

**Table 21: Biogenic Carbon Content**

| Indicator                           | Unit | A1-A3    |
|-------------------------------------|------|----------|
| Biogenic carbon content - product   | kg   | 0.00E+00 |
| Biogenic carbon content - packaging | kg   | 1.70E-03 |

Note: 1 kg biogenic carbon is equivalent to 44/12 kg CO<sub>2</sub>

**Table 22: EN15804+A1 Environmental Impact Indicators**

| Indicator         | Unit                                  | A1-A3    | C1       | C2        | C3       | C4       | D         |
|-------------------|---------------------------------------|----------|----------|-----------|----------|----------|-----------|
| GWP (EN15804+A1)  | kg CO <sub>2</sub> -eq.               | 1.30E+01 | 6.63E-03 | 6.97E-02  | 4.92E-02 | 1.45E-03 | -3.11E+00 |
| ODP (EN15804+A1)  | kg CFC11-eq.                          | 1.98E-09 | 7.89E-16 | 8.37E-15  | 1.07E-14 | 1.72E-16 | 5.52E-11  |
| AP (EN15804+A1)   | kg SO <sub>2</sub> -eq.               | 1.20E-01 | 2.75E-05 | 3.55E-04  | 2.02E-04 | 6.00E-06 | -2.28E-02 |
| EP (EN15804+A1)   | kg PO <sub>4</sub> <sup>3-</sup> -eq. | 6.53E-03 | 6.55E-06 | 8.87E-05  | 4.77E-05 | 1.43E-06 | -8.45E-04 |
| POCP (EN15804+A1) | kg Ethene.                            | 6.14E-03 | 2.99E-06 | -1.24E-04 | 2.16E-05 | 6.52E-07 | -1.47E-03 |
| ADPE (EN15804+A1) | kg Sb-eq.                             | 4.01E-04 | 8.83E-11 | 9.36E-10  | 8.60E-10 | 1.93E-11 | -6.80E-06 |
| ADPF (EN15804+A1) | MJ                                    | 1.63E+02 | 8.78E-02 | 9.32E-01  | 6.47E-01 | 1.92E-02 | -3.68E+01 |

## Results for additional scenarios

This section provides results for alternate end-of-life scenarios.

**Table 23: EN15804+A2 Core environmental impact indicators**

| Indicator               | Unit                        | 100% Recycling |          |           | 100% Landfilling |          |           |
|-------------------------|-----------------------------|----------------|----------|-----------|------------------|----------|-----------|
|                         |                             | C3             | C4       | D         | C3               | C4       | D         |
| GWP-total               | kg CO <sub>2</sub> -eq.     | 5.85E-02       | 0.00E+00 | -4.48E+00 | 0.00E+00         | 9.75E-03 | 4.50E+00  |
| GWP-fossil              | kg CO <sub>2</sub> -eq.     | 5.85E-02       | 0.00E+00 | -4.49E+00 | 0.00E+00         | 9.75E-03 | 4.51E+00  |
| GWP-biogenic            | kg CO <sub>2</sub> -eq.     | 2.11E-05       | 0.00E+00 | 1.08E-02  | 0.00E+00         | 1.44E-06 | -1.09E-02 |
| GWP-luluc               | kg CO <sub>2</sub> -eq.     | 1.85E-06       | 0.00E+00 | -4.79E-04 | 0.00E+00         | 2.56E-07 | 4.81E-04  |
| ODP                     | kg CFC11-eq.                | 1.07E-14       | 0.00E+00 | 6.71E-11  | 0.00E+00         | 9.75E-16 | -6.73E-11 |
| AP                      | Mole of H+ eq.              | 3.43E-04       | 0.00E+00 | -3.73E-02 | 0.00E+00         | 5.78E-05 | 3.74E-02  |
| EP-freshwater           | kg P eq.                    | 1.67E-08       | 0.00E+00 | -3.95E-07 | 0.00E+00         | 1.50E-09 | 3.97E-07  |
| EP-marine               | kg N eq.                    | 1.66E-04       | 0.00E+00 | -3.60E-03 | 0.00E+00         | 2.84E-05 | 3.62E-03  |
| EP-terrestrial          | Mole of N eq.               | 1.83E-03       | 0.00E+00 | -3.81E-02 | 0.00E+00         | 3.11E-04 | 3.83E-02  |
| POCP                    | kg NMVOC eq.                | 4.48E-04       | 0.00E+00 | -1.18E-02 | 0.00E+00         | 7.67E-05 | 1.19E-02  |
| ADP-m&m <sup>1</sup>    | kg Sb-eq.                   | 1.01E-09       | 0.00E+00 | -9.73E-06 | 0.00E+00         | 1.28E-10 | 9.77E-06  |
| ADP-fossil <sup>1</sup> | MJ                          | 7.67E-01       | 0.00E+00 | -5.17E+01 | 0.00E+00         | 1.29E-01 | 5.19E+01  |
| WDP <sup>1</sup>        | m <sup>3</sup> world equiv. | 3.31E-03       | 0.00E+00 | 1.44E-02  | 0.00E+00         | 3.66E-05 | -1.45E-02 |

**Table 24: EN15804+A2 Additional Environmental Impact Indicators**

| Indicator                       | Unit                    | 100% Recycling |          |           | 100% Landfilling |          |           |
|---------------------------------|-------------------------|----------------|----------|-----------|------------------|----------|-----------|
|                                 |                         | C3             | C4       | D         | C3               | C4       | D         |
| GWP-GHG <sup>2</sup>            | kg CO <sub>2</sub> -eq. | 5.85E-02       | 0.00E+00 | -4.49E+00 | 0.00E+00         | 9.75E-03 | 4.51E+00  |
| GWP-GHG (IPCC AR5) <sup>3</sup> | kg CO <sub>2</sub> -eq. | 5.85E-02       | 0.00E+00 | -4.49E+00 | 0.00E+00         | 9.75E-03 | 4.51E+00  |
| PM                              | Disease incidences      | 6.74E-09       | 0.00E+00 | -1.26E-07 | 0.00E+00         | 1.16E-09 | 1.26E-07  |
| IRP <sup>4</sup>                | kBq U235 eq.            | 1.72E-05       | 0.00E+00 | 3.88E-02  | 0.00E+00         | 2.69E-06 | -3.89E-02 |
| ETP-fw <sup>1</sup>             | CTUe                    | 5.19E-01       | 0.00E+00 | -1.06E+00 | 0.00E+00         | 5.74E-02 | 1.06E+00  |
| HTP-c <sup>1</sup>              | CTUh                    | 6.51E-12       | 0.00E+00 | 5.81E-10  | 0.00E+00         | 9.44E-13 | -5.83E-10 |
| HTP-nc <sup>1</sup>             | CTUh                    | 1.20E-10       | 0.00E+00 | -3.08E-09 | 0.00E+00         | 2.07E-11 | 3.09E-09  |
| SQP                             | Pt                      | 1.65E-02       | 0.00E+00 | -4.38E+00 | 0.00E+00         | 2.62E-04 | 4.39E+00  |

**Table 25: Use of resources**

| Indicator | Unit           | 100% Recycling |          |           | 100% Landfilling |          |           |
|-----------|----------------|----------------|----------|-----------|------------------|----------|-----------|
|           |                | C3             | C4       | D         | C3               | C4       | D         |
| PERE      | MJ             | 1.14E-01       | 0.00E+00 | 6.88E-01  | 0.00E+00         | 5.57E-04 | -6.91E-01 |
| PERM      | MJ             | 0.00E+00       | 0.00E+00 | 0.00E+00  | 0.00E+00         | 0.00E+00 | 0.00E+00  |
| PERT      | MJ             | 1.14E-01       | 0.00E+00 | 6.88E-01  | 0.00E+00         | 5.57E-04 | -6.91E-01 |
| PENRE     | MJ             | 7.67E-01       | 0.00E+00 | -5.17E+01 | 0.00E+00         | 1.29E-01 | 5.19E+01  |
| PENRM     | MJ             | 0.00E+00       | 0.00E+00 | 0.00E+00  | 0.00E+00         | 0.00E+00 | 0.00E+00  |
| PENRT     | MJ             | 7.67E-01       | 0.00E+00 | -5.17E+01 | 0.00E+00         | 1.29E-01 | 5.19E+01  |
| SM        | kg             | 0.00E+00       | 0.00E+00 | 0.00E+00  | 0.00E+00         | 0.00E+00 | 0.00E+00  |
| RSF       | MJ             | 0.00E+00       | 0.00E+00 | 0.00E+00  | 0.00E+00         | 0.00E+00 | 0.00E+00  |
| NRSF      | MJ             | 0.00E+00       | 0.00E+00 | 0.00E+00  | 0.00E+00         | 0.00E+00 | 0.00E+00  |
| FW        | m <sup>3</sup> | 2.30E-04       | 0.00E+00 | -1.58E-01 | 0.00E+00         | 7.45E-07 | 1.58E-01  |

# Environmental Product Declaration

AXXIS® 0.75mm from New Zealand Steel

**Table 26: Waste production and output flows**

| Indicator | Unit | 100% Recycling |          |           | 100% Landfilling |          |           |
|-----------|------|----------------|----------|-----------|------------------|----------|-----------|
|           |      | C3             | C4       | D         | C3               | C4       | D         |
| HWD       | kg   | 3.83E-11       | 0.00E+00 | -1.40E-07 | 0.00E+00         | 2.07E-12 | 1.41E-07  |
| NHWD      | kg   | 3.60E-05       | 0.00E+00 | 5.44E-03  | 0.00E+00         | 6.19E+00 | -5.46E-03 |
| RWD       | kg   | 1.57E-07       | 0.00E+00 | 9.10E-06  | 0.00E+00         | 2.51E-08 | -9.13E-06 |
| CRU       | kg   | 0.00E+00       | 0.00E+00 | 0.00E+00  | 0.00E+00         | 0.00E+00 | 0.00E+00  |
| MFR       | kg   | 6.19E+00       | 0.00E+00 | 0.00E+00  | 0.00E+00         | 0.00E+00 | 0.00E+00  |
| MER       | kg   | 0.00E+00       | 0.00E+00 | 0.00E+00  | 0.00E+00         | 0.00E+00 | 0.00E+00  |
| EEE       | MJ   | 0.00E+00       | 0.00E+00 | 0.00E+00  | 0.00E+00         | 0.00E+00 | 0.00E+00  |
| EET       | MJ   | 0.00E+00       | 0.00E+00 | 0.00E+00  | 0.00E+00         | 0.00E+00 | 0.00E+00  |

**Table 27: EN15804+A1 Environmental Impact Indicators**

| Indicator         | Unit                                  | 100% Recycling |          |           | 100% Landfilling |          |           |
|-------------------|---------------------------------------|----------------|----------|-----------|------------------|----------|-----------|
|                   |                                       | C3             | C4       | D         | C3               | C4       | D         |
| GWP (EN15804+A1)  | kg CO <sub>2</sub> -eq.               | 5.79E-02       | 0.00E+00 | -4.45E+00 | 0.00E+00         | 9.65E-03 | 4.46E+00  |
| ODP (EN15804+A1)  | kg CFC11-eq.                          | 1.26E-14       | 0.00E+00 | 7.89E-11  | 0.00E+00         | 1.15E-15 | -7.92E-11 |
| AP (EN15804+A1)   | kg SO <sub>2</sub> -eq.               | 2.37E-04       | 0.00E+00 | -3.25E-02 | 0.00E+00         | 4.00E-05 | 3.27E-02  |
| EP (EN15804+A1)   | kg PO <sub>4</sub> <sup>3-</sup> -eq. | 5.61E-05       | 0.00E+00 | -1.21E-03 | 0.00E+00         | 9.53E-06 | 1.21E-03  |
| POCP (EN15804+A1) | kg Ethene.                            | 2.54E-05       | 0.00E+00 | -2.11E-03 | 0.00E+00         | 4.34E-06 | 2.12E-03  |
| ADPE (EN15804+A1) | kg Sb-eq.                             | 1.01E-09       | 0.00E+00 | -9.73E-06 | 0.00E+00         | 1.28E-10 | 9.77E-06  |
| ADPF (EN15804+A1) | MJ                                    | 7.61E-01       | 0.00E+00 | -5.26E+01 | 0.00E+00         | 1.28E-01 | 5.28E+01  |

## Additional environmental information

### Rollforming

AXXIS® steel is supplied by New Zealand Steel to downstream processors in coil form. These coils are uncoiled, slit, and formed into roof, wall and floor framing components using rollforming machines.

To provide indicative results for the final formed product up to the rollforming gate, data has been obtained from selected sites of several rollformers based in New Zealand. We indicatively estimate that rollforming would add 2.2 kg CO<sub>2</sub>e/m<sup>2</sup> to the results in Table 17.

The indicative factor represents an average of the data collected from the surveyed sites only. These results may not be representative of the final formed product from any particular rollforming operation, company or site. Actual results will vary depending on a range of factors specific to the particular operation of the downstream processors.

## Abbreviations

|               |                                                               |
|---------------|---------------------------------------------------------------|
| <b>ANZSIC</b> | Australian and New Zealand Standard Industrial Classification |
| <b>AS</b>     | Standards Australia                                           |
| <b>AS/NZS</b> | Australian/New Zealand Standard                               |
| <b>CEN</b>    | European Committee for Standardization                        |
| <b>CPC</b>    | Central product classification                                |
| <b>EAFF</b>   | Electric Arc Furnace                                          |
| <b>EF</b>     | Environmental Footprint                                       |
| <b>EN</b>     | European Norm (Standard)                                      |
| <b>GPI</b>    | General Programme Instructions                                |
| <b>HERA</b>   | Heavy Engineering Research Association                        |
| <b>ISO</b>    | International Organization for Standardization                |
| <b>KOBM</b>   | Klockner Oxygen Blown Maxhutte.                               |
| <b>LCA FE</b> | Life Cycle for Experts                                        |
| <b>LCI</b>    | Life Cycle Inventory                                          |
| <b>MBIE</b>   | Ministry of Business, Innovation, and Employment              |
| <b>MHF</b>    | Multi Hearth Furnace                                          |
| <b>MLC</b>    | Managed LCA Content                                           |
| <b>ND</b>     | Not Declared                                                  |
| <b>NZ</b>     | New Zealand                                                   |
| <b>NZS</b>    | New Zealand Steel                                             |
| <b>SVHC</b>   | Substance of Very High Concern                                |
| <b>VRU</b>    | Vanadium Recovery Unit                                        |

## References

---

**AS. (2011). 1397.** Continuous hot-dip metallic coated steel sheet and strip - Coatings of zinc and zinc alloyed with aluminium and magnesium. Standards Australia.

---

**AS. (1996). 1365.** Tolerances for flat-rolled steel products. Standards Australia.

---

**BraveTrace. (2023).** NZECS Residual Supply Mix for electricity certification. New Zealand.

---

**CEN. (2013).** EN 15804:2012+A1:2013, Sustainability of construction works - Environmental product declarations - Core rules for the product category of construction products. European Committee for Standardization.

---

**CEN. (2021).** EN 15804:2012+A2:2019/AC:2021 Sustainability of construction works. Environmental product declarations. Core rules for the product category of construction products. Brussels: European Committee for Standardization.

---

**CEN. (2024).** EN 15941:2024, Sustainability of construction works – Data quality for environmental assessment of products and construction work – Selection and use of data. Brussels: European Committee for Standardization.

---

**ECHA. (2025).** Candidate List of substances of very high concern for Authorisation. Retrieved from European Chemical Agency: <https://echa.europa.eu/candidate-list-table>

---

**ECO Platform. (2024).** ECO Platform standards, versions published 2024-12-20. Retrieved from <https://www.eco-platform.org/our-documents.html>.

---

**EPD International. (2025a).** General Programme Instructions for the International EPD System. Version 5.0.1, dated 2025-02-27. Stockholm: EPD International AB.

---

**EPD International. (2025b).** PCR 2019:14 Construction Products version 2.0.1 of 2025-06-05 (valid until 2030-04-07). Stockholm: EPD International AB.

---

---

**IPCC. (2013).** Climate Change 2013: The Physical Science Basis. Geneva, Switzerland: IPCC.

---

**ISO. (2006a).** ISO 14040: Environmental management – Life cycle assessment – Principles and framework. Geneva: International Organization for Standardization.

---

**ISO. (2006b).** ISO 14044: Environmental management – Life cycle assessment – Requirements and guidelines. Geneva: International Organization for Standardization.

---

**ISO. (2006c).** ISO 14025: Environmental labels and declarations - Type III environmental declarations - Principles and procedures. Geneva: International Organization for Standardization.

---

**MBIE. (2023).** Annual Electricity Data Updates. New Zealand: Ministry of Business, Innovation, and Employment.

---

**RNZ. (2024).** Carbon saved by NZ Steel's new furnace upped to 1 million tonnes a year, brought forward to 2025. Retrieved from <https://www.rnz.co.nz/news/business/526540/carbon-saved-by-nz-steel-s-new-furnace-upped-to-1-million-tonnes-a-year-brought-forward-to-2025>

---

**Sphera. (2024).** Life Cycle Inventory Database 2024 Documentation. Retrieved from Sphera: <https://lcadatabase.sphera.com/>

---

**thinkstep-anz. (2021).** HERA Report R5-89: Steel recycling, v.2. New Zealand: HERA.

---

## Environmental Product Declaration

AXXIS® 0.75mm from New Zealand Steel

# General Information

An Environmental Product Declaration, or EPD, is a standardised and verified way of quantifying the environmental impacts of a product based on a consistent set of rules known as a PCR (Product Category Rules). The EPD owner has the sole ownership, liability, and responsibility for the EPD.

EPDs within the same product category but published in different EPD programmes may not be comparable. For two EPDs to be comparable, they shall be based on the same PCR (including the same first-digit version number) or be based on fully-aligned PCRs or versions of PCRs; cover products with identical functions, technical performances and use (e.g. identical declared/functional units); have identical scope in terms of included life-cycle stages (unless the excluded life-cycle stage is demonstrated to be insignificant); apply identical impact assessment methods (including the same version of characterisation factors); and be valid at the time of comparison. For further information about comparability, see EN 15804 (CEN, 2021) and ISO 14025 (ISO, 2006c).

The results for EN15804+A1 (CEN, 2013) compliant EPDs are not comparable with EN15804+A2 (CEN, 2021) compliant studies as the methodologies are different. To support backwards comparability and compatibility, environmental performance results have also been provided for the indicators required in EN15804+A1, although the study does not claim compliance with this standard.

| Programme Information                                                                                                                         |                                                                                                                                                                                                                                                                                                                                                                                                                                         |
|-----------------------------------------------------------------------------------------------------------------------------------------------|-----------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------|
| EPD Programme Operator:                                                                                                                       | <b>EPD International AB</b><br>Web: <a href="http://www.environdec.com">www.environdec.com</a><br>Email: <a href="mailto:support@environdec.com">support@environdec.com</a><br>Post: EPD International AB, Box 210 60, SE-100 31 Stockholm, Sweden<br>                                                                                              |
| Licensee:                                                                                                                                     | <b>EPD Australasia Limited</b><br>Web: <a href="http://www.epd-australasia.com">www.epd-australasia.com</a><br>Email: <a href="mailto:info@epd-australasia.com">info@epd-australasia.com</a><br>Post: EPD Australasia Limited, 6 Cube Court, Richmond 7020, New Zealand<br>                                                                        |
| <b>Product Category Rules (PCR)</b> CEN standard EN 15804 serve as the core Product Category Rules (PCR)                                      |                                                                                                                                                                                                                                                                                                                                                                                                                                         |
| PCR:                                                                                                                                          | PCR 2019.14 Construction Products, version 2.0.1<br>(published on 2025-06-05, valid until 2030-04-07)                                                                                                                                                                                                                                                                                                                                   |
| PCR review conducted by:                                                                                                                      | The Technical Committee of the International EPD® System.<br>See <a href="http://www.environdec.com">www.environdec.com</a> for a list of members.                                                                                                                                                                                                                                                                                      |
| Review Chairs:                                                                                                                                | Rob Rouwette, start2see (chair), Noa Meron, thinkstep-anz (co-chair).<br>The review panel may be contacted via the Secretariat:<br><a href="http://www.environdec.com/contact">www.environdec.com/contact</a>                                                                                                                                                                                                                           |
| Verification                                                                                                                                  |                                                                                                                                                                                                                                                                                                                                                                                                                                         |
| External and independent ('third-party') verification of the declaration and data, according to ISO 14025:2006, via EPD verification through: | <input checked="" type="checkbox"/> Individual EPD verification without a pre-verified LCA/EPD tool<br><input type="checkbox"/> Individual EPD verification with a pre-verified LCA/EPD tool<br><input type="checkbox"/> EPD Process Certification* without a pre-verified LCA/EPD tool<br><input type="checkbox"/> EPD Process Certification* with a pre-verified LCA/EPD tool<br><input type="checkbox"/> Fully pre-verified EPD tool |
| Third-party verifier:                                                                                                                         | <br><b>Rob Rouwette, start2see Pty Ltd</b><br>Web: <a href="http://www.start2see.com.au">www.start2see.com.au</a><br>Email: <a href="mailto:Rob.Rouwette@start2see.com.au">Rob.Rouwette@start2see.com.au</a>                                                                                                                                         |
| Verifier approved by:                                                                                                                         | <b>EPD Australasia Ltd and The International EPD System</b>                                                                                                                                                                                                                                                                                                                                                                             |
| Procedure for follow-up during EPD validity involves third party verifier:                                                                    | <input checked="" type="checkbox"/> Yes<br><input type="checkbox"/> No                                                                                                                                                                                                                                                                                                                                                                  |



**NOTE:** Buyers and users of New Zealand Steel Limited products and services must make their own assessment of the products for their own conditions. All queries regarding product specification, purpose or application should be directed to New Zealand Steel Limited, phone 0800 697 833. New Zealand Steel Limited reserves the right to modify products, techniques, equipment and statements to reflect improvements in the manufacture and application of its products. The information contained in this brochure is accurate as at May 2026 and supplied without prejudice to New Zealand Steel Limited's standard terms and conditions of sale. In the event of conflict between this information and the standard terms and conditions, the standard terms and conditions prevail. This brochure supersedes all previous brochure editions. AXXIS® is a trademark of New Zealand Steel Limited. Copyright© New Zealand Steel Limited. May 2026.

**NZSTEEL.CO.NZ**

